




High quality tool steel, premium service
and engineering for

Extrusion Industry

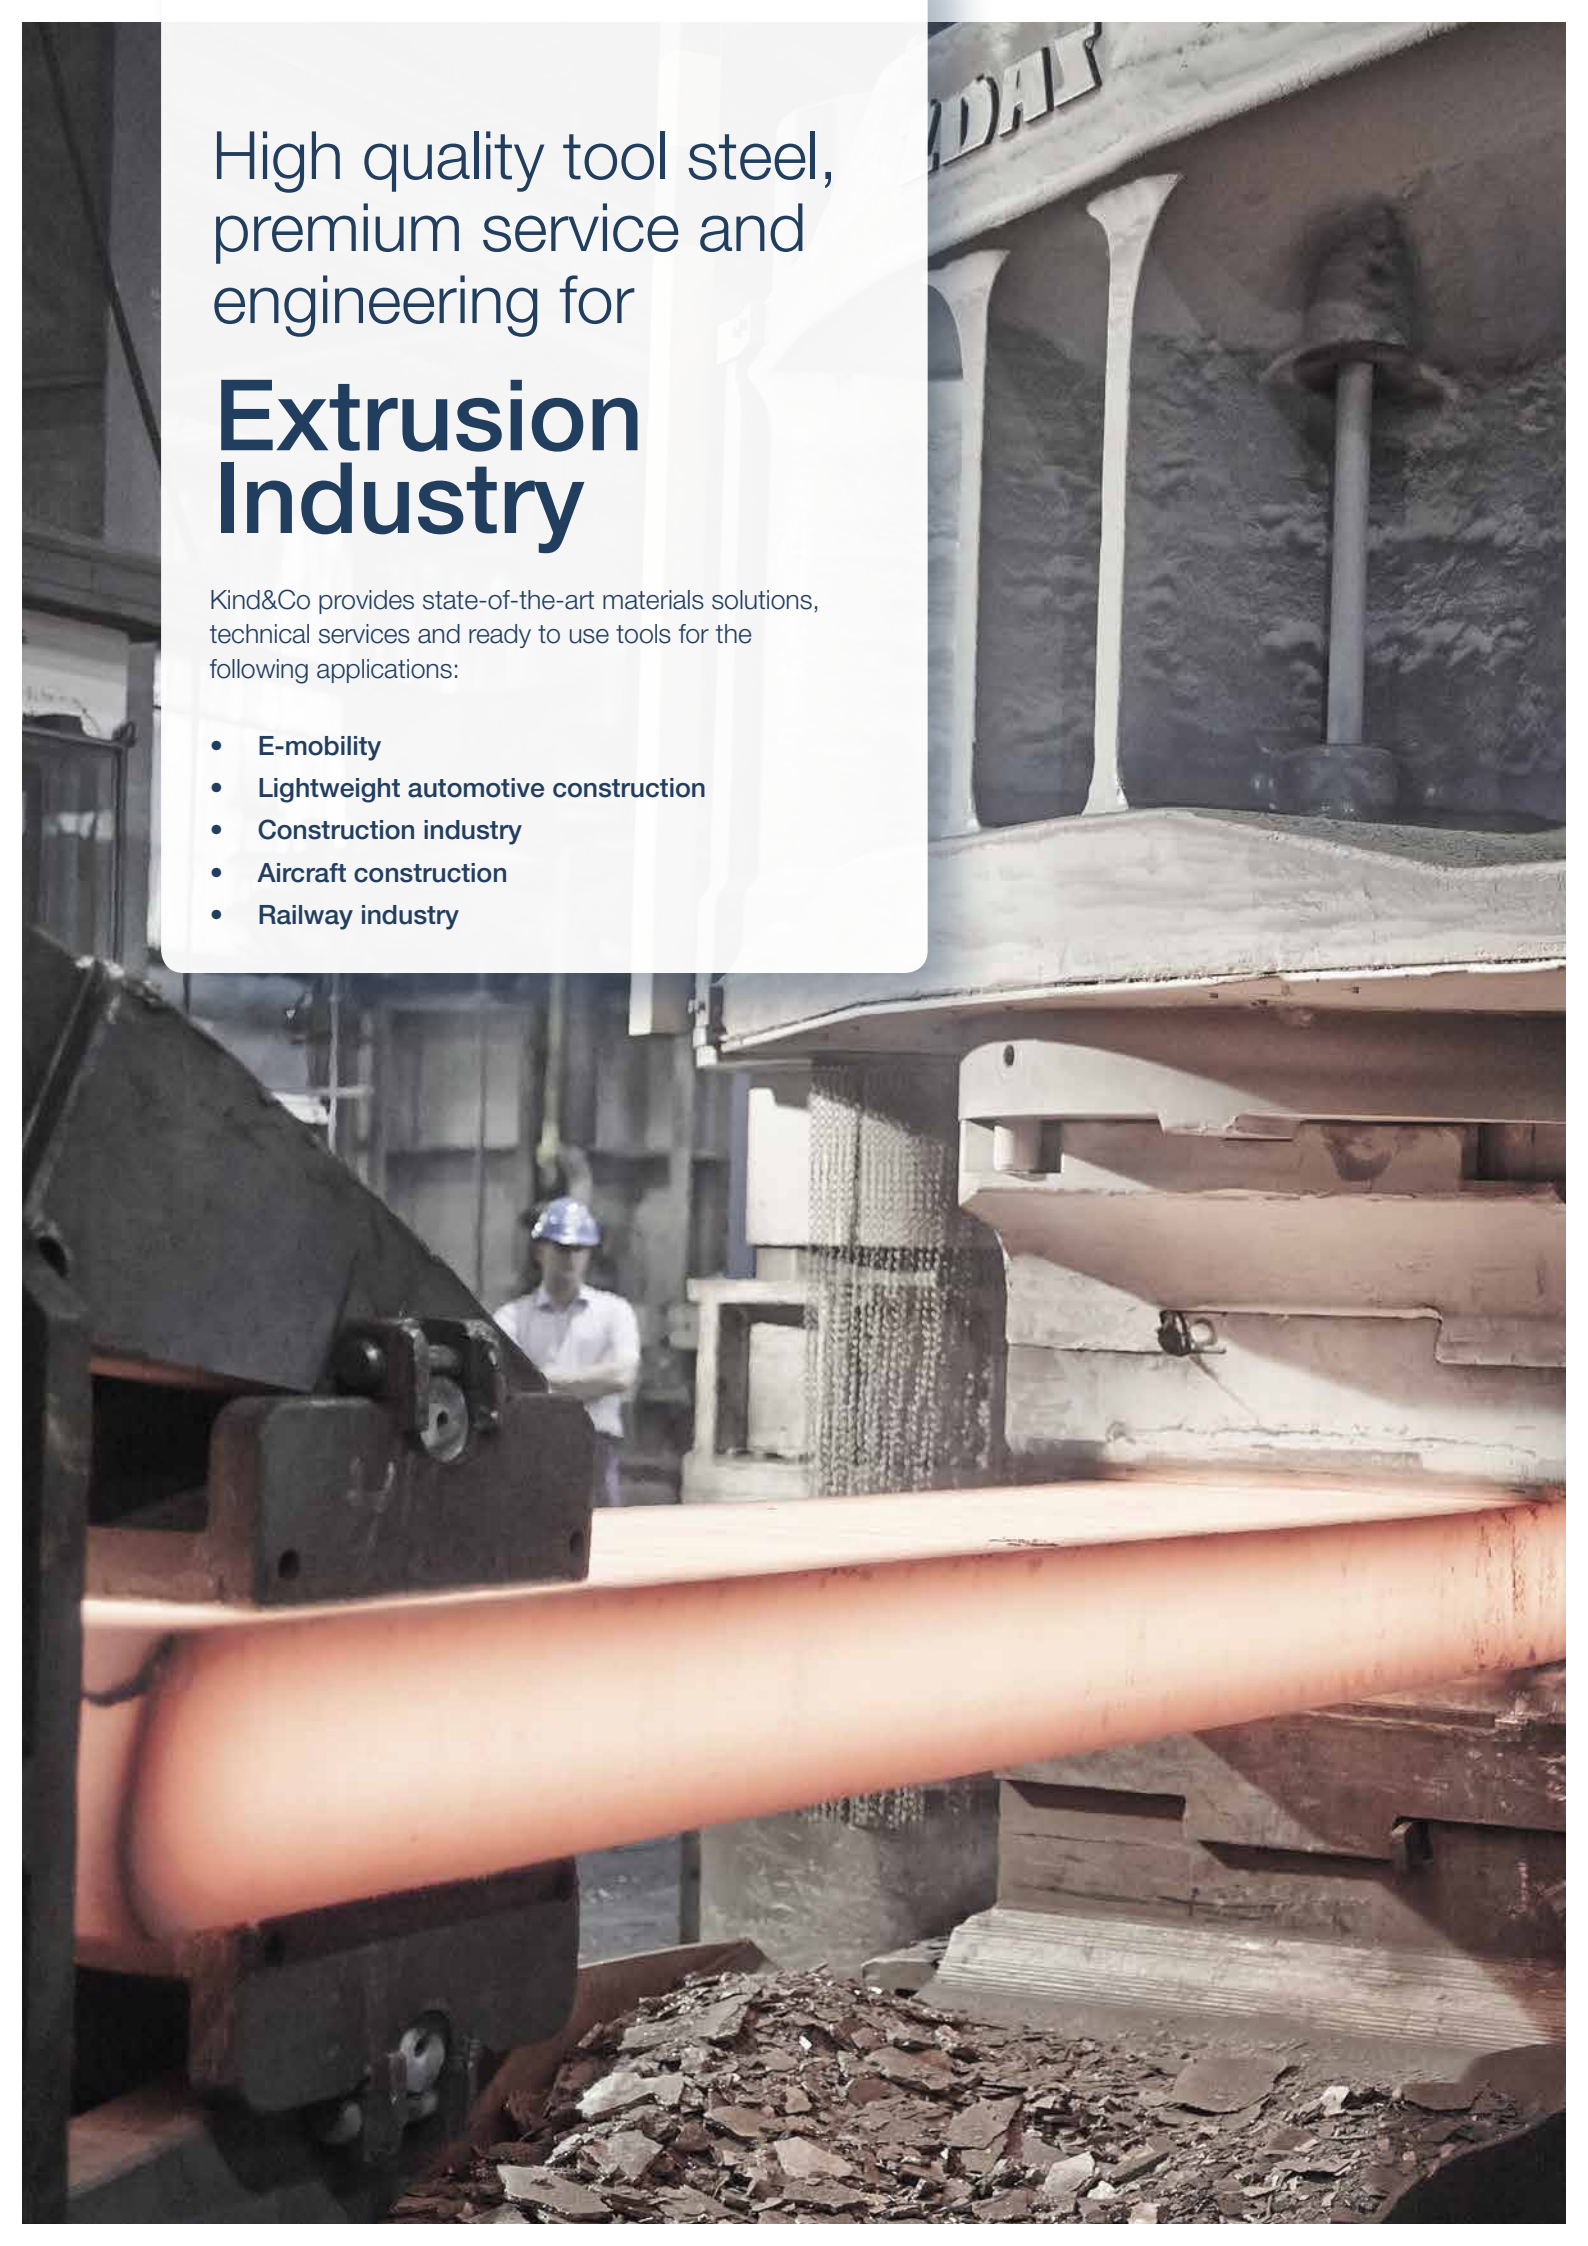

High quality tool steel,
premium service and
engineering for

Extrusion Industry

Kind&Co provides state-of-the-art materials solutions,
technical services and ready to use tools for the
following applications:

- **E-mobility**
- **Lightweight automotive construction**
- **Construction industry**
- **Aircraft construction**
- **Railway industry**

Kind&Co

For more than 130 years, we have been producing high quality tool steel exclusively at our traditional location. Even today, Kind&Co is still a wholly-owned family company. We stand for sophisticated material solutions, maximum quality, reliable service and competent advice – tailored to the individual purpose. We have particularly strong application expertise in the segments of extrusion, pressure die casting and die forging.

Extrusion

The versatility of extrusion practically knows no boundaries. Almost no other process is so versatile when it comes to hot forming so many metals. The range of applications for extruded products is extremely varied.

For example, aluminium alloys that are relatively simple to extrude are used in aircraft, automotive and railway industry. New applications such as e-mobility and the continued need for lightweight automotive construction demands new material concepts to satisfy such requirements.

We offer new solutions for these applications with our current, in-house developments such as TQ1, Q10, HP1 or HTR. Since 2016 we have introduced our special hot-work tool steel CS1 for the extrusion industry.



Forging of ESR ingot on the 30MN-press ▲

Technical advice

Our team of specialist application engineers provides service in selecting of correct tool steel. The objective is to specify the correct tool steel along with the ideal features for your specific application together with you.

Service

We also use FEM-Analysis to optimize tool design with the objective of continuously improving performance and life time across the entire process. We provide recommendations for you based on the results of our investigations on damaged or worn out tools.

We provide innovated tool steel solutions for the extrusion industry with the aid of our relining centre, the database system, the database which has existed for more than 20 years.

Electro-slag remelting process (ESR) ▼



Our products

In extrusion, we are the market leader as a complete supplier of ready-to-use tools.

	Individual forged (liner, 3d)	Pre-machined	Finished products (drawing)	Heat treatment	Relining service, repairs
Mantle	●	●	●	●	●
Intermediate liner	●	●	●	●	●
Inner liner	●	●	●	●	●
Stem	●	●	●	●	●
Mandrel	●	●	●	●	●
Die		●	●	●	
Bolster	●	●	●	●	
Die holder	●	●	●	●	
Dummy block, cleaning disc		●	●	●	

Technical advice and service

Our experienced team of engineers, application experts and production specialists offers you the following services:

1. Construction / design

- FEM-Analysis and process simulations
- Changing the billet lengths and diameters on the containers

2. Material selection

- Technical advice
- Application-specific special steels

3. Inspection

- Hardness test
- Crack test
- Dimensions test
- Ultrasonic test
- Magnetic powder test
- Analysis

4. Service

- Repair work / welding
- Welding sealing surfaces
- Honing

5. Damage analysis

- Usage evaluation
- Comprehensive damage diagnostics

Shrinkage process
on container ▼



Mandrels ▼




▲ Container for aluminium extrusion with Q10 inner sleeve




Hardness test on container ▲

USN, USD, RPU, PWM, AISI 4340

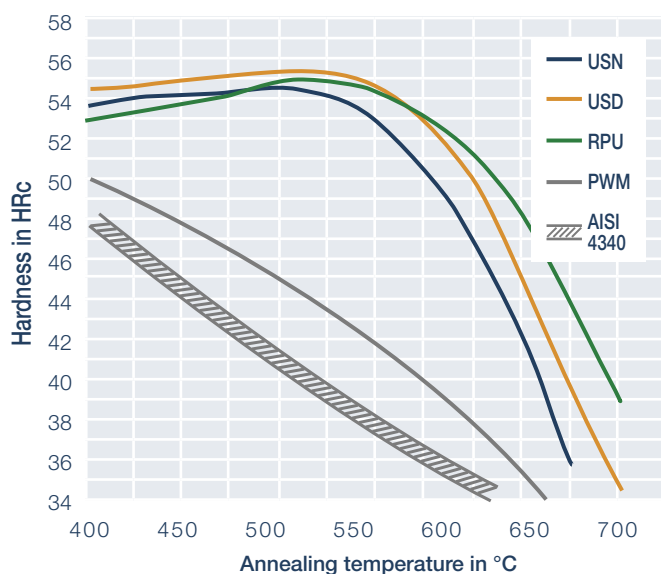

- The classic USN and USD hot-work steels are characterised by high-temperature strength and excellent toughness.
- Hot-work tool steel RPU is recommended if there are more stringent requirements regarding high-temperature strength and temper resistance.
- Due to higher process related requirements, the lower-alloyed tool steels PWM and AISI 4340 are not recommended for this application.


TQ1, HP1, HTR, CS1

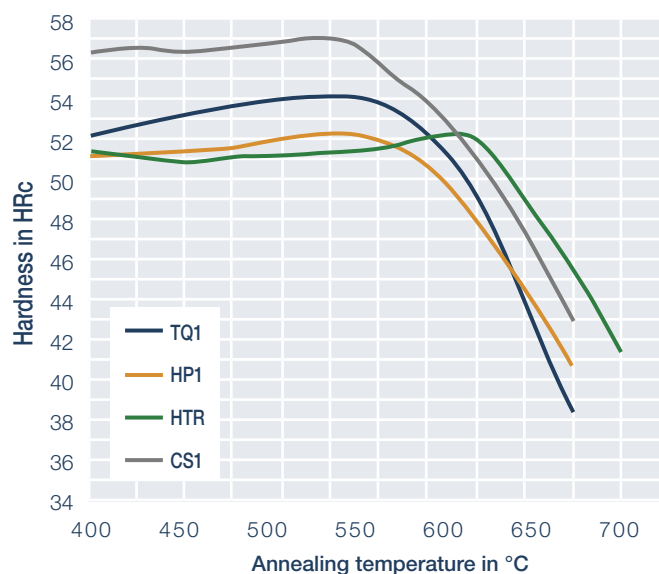

The special tool steels from our own development are based on the principle of greatest cleanliness.

- TQ1 and HP1 are characterised by the combination of high temperature strength combined with high toughness.
- HTR was developed for requirements that demand extremely great high-temperature strength and/or thermal conductivity.
- For more demanding special applications in the 55-57 HRc hardness range, we've developed the new CS1 high-performance steel.


HWD, HMoD, RM10Co

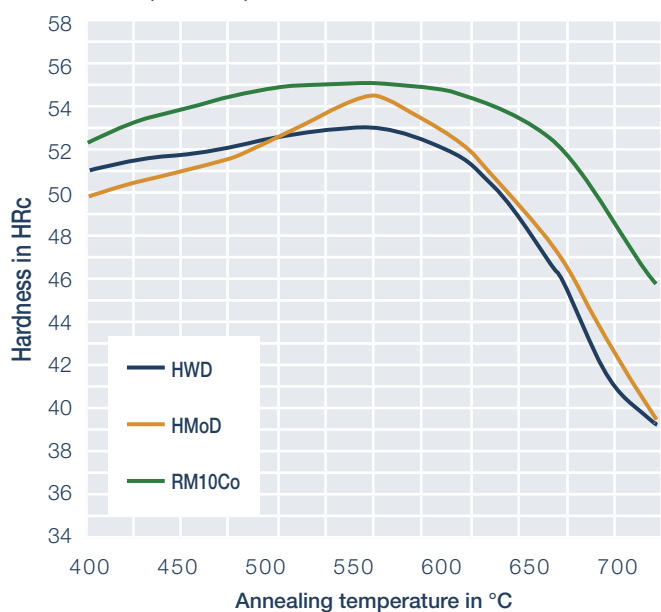

The special steels from our own development are based on the principle of greatest purity.

- TQ1 and HP1 are characterised by the combination of high temperature strength combined with high toughness.
- HTR was developed for applications that require extremely high levels of temperature strength and thermal conductivity.
- Thanks to its superior tenacity behaviour, HMoD is preferred for water-cooled tools.

SA718, SA50Ni, HWF

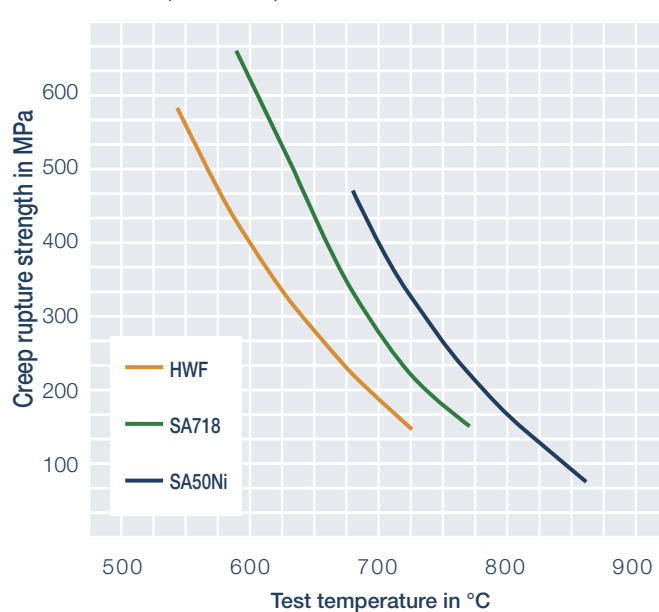

- HWF is an austenitic, curable steel for inner liner, dies, or die holders that face particularly high temperatures.
- With the SA 718 for inner liner in the container during extrusion of brass, copper, and copper-nickel alloys, it is possible to achieve considerable improvements in durability.
- The material SA 50Ni has an extremely high temperature strength and is preferred in use for dies, mandrel tips, and pressure discs.

Overview of the most important materials for tool technology during extrusion

Martensitic

Brand name	Mat. no.	Short name	AISI	AFNOR	Typical analysis % by weight									
					C	Si	Mn	Cr	Mo	Ni	V	W	Co	
USN	1.2343	X37CrMoV5-1	H 11	Z38CDV5	0,37	1,00	0,40	5,20	1,20	-	0,40	-	-	-
USD	1.2344	X40CrMoV5-1	H 13	Z40CDV5	0,40	1,00	0,40	5,20	1,30	-	1,00	-	-	-
USD-H	1.2345	X50CrMoV5-1	-	-	0,51	0,85	0,30	4,90	1,35	-	0,90	-	-	-
RP	1.2365	32CrMoV12-28	-	32DCV12-28	0,32	0,40	0,40	3,00	2,80	-	0,50	-	-	-
RPU	1.2367	X38CrMoV5-3	-	Z38VDV5-3	0,38	0,40	0,40	5,00	3,00	-	0,60	-	-	-
MA**	1.2581	X30WCrV9-3	H 21	-	0,30	0,30	0,30	2,70	-	-	0,35	9,00	-	-
HWD**	1.2678	X45CoCrWV5-5-5	H 19	Z40KCWW05-05-05	0,40	0,30	0,40	4,50	0,50	-	2,10	4,50	4,50	-
PWM	1.2714	55NiCrMoV7	~L6	55NCDV7	0,55	0,30	0,80	1,10	0,45	1,70	0,10	-	-	-
N400	1.2767	45NiCrMo16	~6F7	45NCD16	0,45	0,25	0,40	1,35	0,25	4,00	-	-	-	-
RPCo**	1.2885	X32CrMoCoV3-3-3	H 10A	-	0,32	0,40	0,40	3,00	2,80	-	0,60	-	3,00	-
RM 10 Co**	1.2888	X20CoCrWMo10-9	-	-	0,20	0,20	0,50	9,50	2,00	-	-	5,50	10,00	-
HMoD**	1.2889	X45CoCrMoV5-5-3	H 19A	-	0,45	0,30	0,40	4,50	3,00	-	2,00	-	4,50	-
CR7V-L	Spezial	-	-	-	0,42	0,50	0,40	6,50	1,30	-	0,80	-	-	-
CS1*	Spezial	-	-	-	0,50	0,30	0,40	5,00	1,90	-	0,55	-	-	Nb +
GSF	Spezial	-	-	-	0,28	0,30	0,70	2,80	0,60	1,00	0,40	-	-	-
HP1*	Spezial	-	-	-	0,35	0,20	0,30	5,20	1,40	-	0,55	-	-	Nb +
HTR	Spezial	-	-	-	0,32	0,20	0,30	2,20	1,20	-	0,50	3,80	-	-
TQ1*/Q10	Spezial	-	-	-	0,36	0,25	0,40	5,20	1,90	-	0,55	-	-	-

Austenitic

Brand name	Mat. no.	Short name	AISI	AFNOR	Typical analysis % by weight									
					C	Si	Mn	Cr	Mo	Ni	V	W	Co	
AWS**	1.2731	X50NiCrWV13-13	-	-	0,50	1,40	0,70	13,00	-	13,00	0,60	2,40	-	-
MA-Rekord**	1.2758	X50WNiCrVCo12-12	-	-	0,55	1,40	0,70	4,00	0,60	11,50	1,10	12,00	1,50	-
HWF**	1.2779	X6NiCrTi26-15	A286	Z6NCTDV25 15B	<0,08	<1,00	1,10	15,00	1,50	26,00	-	-	-	Ti2,10


Nickel-based alloy

Brand name	Mat. no.	Short name	AISI	AFNOR	Typical analysis % by weight									
					C	Si	Mn	Cr	Mo	Ni	V	W	Co	
SA 718**	2.4668	NiCr19Fe19Nb5Mo3	UNS No 7718	NC19FeNb	0,05	<0,35	<0,35	19,00	3,00	53,00	-	-	-	Nb 5,0 Ti 0,9 Al 0,5
SA 50 Ni**	2.4973	NiCr19CoMo	R41	-	<0,12	<0,50	<0,10	19,00	9,50	Rest Balance	-	-	11,00	Ti 3,0 Al 1,6

* produced via the ESR-process

** for heavy metal extrusion only

Material recommendations for light metal extrusion

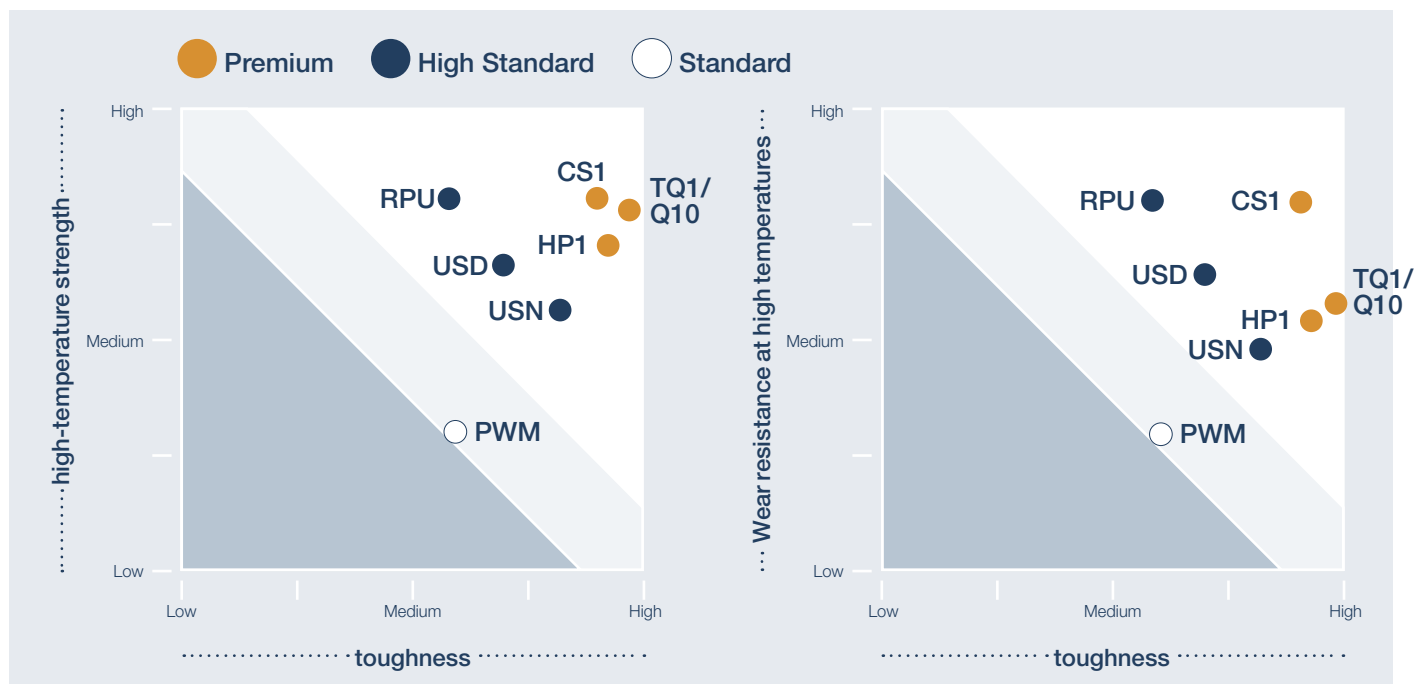


- High standard: standardised alloy concept, but excellent finish at Kind&Co
- Q10 for inner sleeves with exceptional durability, particularly with problems such as deformations on sealing surfaces
- TQ1 or HP1 are suitable for sophisticated extrusion tools and long durability (TCO reduction)
- TQ1 for thin-walled profile geometries - without nitration
- CS1 is of particular interest for frequently used tools, e.g. extrusion punches and dies

Steel grades per product group on light metal including typical hardness (HRc)

HRc	Mantle	Inter-mediate liner	Inner liner	Stem	Die	Bolster	Die holder	Dummy block	Tie rod	Press column
PWM						41-45	41-45		32-38	32-38
GSF							41-45		32-36	32-36
USN*	33-38	40-44	47-50	48-50	47-50	42-45	45-47	48-50	42-45	
RPU*		40-44	47-50	48-51	47-50			47-50		
USD*	33-38	40-44	47-50	48-51	47-51		45-47	48-50		
TQ1/Q10		40-44	51-53	51-53	48-53			51-53		
HP1		40-44	47-51	50-52	47-51			47-51		
CS1			55-57	55-57	50-57			50-57		

* The alloy concept is standardised for our "High Standard" grades.

Material recommendations for heavy metal extrusion

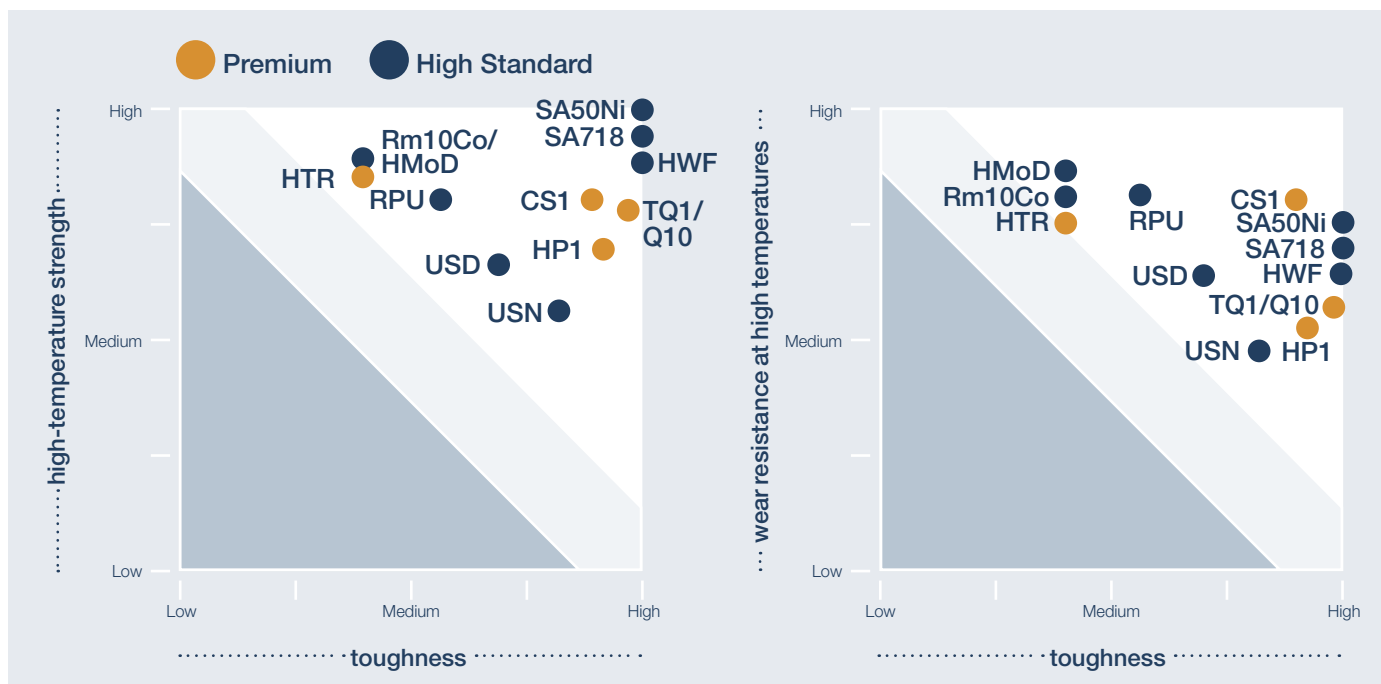

- High Standard: standardised alloy concept, but excellent finish at Kind&Co
- SA 718 inner liner for extrusion of Cu alloys with improved durability compared to HWF
- HTR interim sleeves with excellent temper resistance and enhanced thermal conductivity, successfully combined with SA 718 inner liner

Steel grades for tools made for heavy metal extrusions with details of hardness (HRc)

HRc	Mantle	Inter-mediate liner	Inner liner	Stem	Mandrel/Tip	Bolster	Die	Die holder	Dummy block	Cleaning discs
USN*	33-38			48-50		41-45				45-48
USD*	33-38			48-51	46-50					45-48
RPU*		39-44		48-50	46-50				46-50	45-48
TQ1/Q10				51-53						
CS1				55-57					50-57	
RPCo							45-48	45-48		
RM10Co		44-46	48-50	48-50	45-50		48-50	45-48	48-50	
HWD					45-48		45-48			
HMOD					45-48		45-48			
HTR		39-44					45-48			
AWS							29-34	29-34		
HWF			31-39				31-39	31-39	31-39	
SA718			40-44		40-44			40-44	40-44	
SA50Ni					38-41		38-41			

* The alloy concept is standardised for our "High Standard" grades.

Technical advice and service

We can stimulate various material features, as well as simulate thermal and mechanical loads. This method identifies critical areas on tools, with the potential of

optimization in design and material selection. Experience from many relining orders supported by FEM-simulations lead to optimised tool solutions.

Examples of several design improvements with the aid of FEM-simulations and empirical development steps



FEM-analysis of mechanical pressure

KCPC – Kind & Co. Power Connector

Optimised container lifting device

Examples for optimising temperature management in container



FEM-simulation of temperature distribution in containers

AP-System, Air Protection system

Optimised resistance heating system with various heating zones

A modern container consists of

- Multi-part design
- 1 to 8-zone heating system
- 1 to 4-zone air system
- AP-system (Air Protection system)
- KCPC (Kind & Co. Power Connector)
- Individual shrinkage technology



Example of a modern AP-System (Air Protection)

- The AP-system prevents thermal shock cracks in the mantle.
- Dry and cooled air flow for regulating an uniform temperature level inside the container, which is achieved by AP-system.

Without AP-System




With AP-System



Necessary information for the FEM-simulation

	Container	Stem	Die holder	Mandrel
Pressing force [MN]	●	●	●	●
Specific load [MPa]	●	●	●	●
Temperature of billets [°C]	●	●	●	●
Extrusion cycle time [round billets/h]	●			●
Extrusion time [sec.]	●			●
Temperature of container [°C]	●			●
Ambient Temperature [°C]	●	●	●	

Typical wear on containers on light metal extrusion and possible solutions

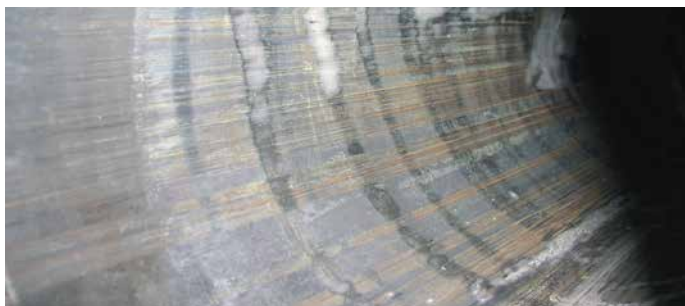

Abrasion or damage to the inner liner bore:

Repair by readjustment of the motion axis of extrusion stem/pressure disc and container;
setting and gap dimension of dummy block



Deformation and cracks on sealing surfaces:

Checking installation position of dies and die holder;
use of special material Q10 with higher hardness and the same level of ductility



Air inclusions between billets and inner liner:

Dimension and hardness testing of liner, intermediate liner in the container and dummy block;
Check burp cycle on the press;
Switch to Q10 inner liner

“The 10 golden rules” from Kind&Co for container design

1. Start extrusion from a container if the temperature $> 380^{\circ}\text{C}$.
2. Homogeneous temperature distribution in the longitudinal direction (aluminium $\pm 25^{\circ}\text{C}$).
3. Multi-part design of the container if $P_{\text{spez}} > 600 \text{ MPa}$.
4. Positive shoulder to inner liners from austenitic steel HWF and to inner liners from SA718 nickel-based alloy.
5. Negative shoulder with martensitic steels (USN, USD, Q10, RPU).
6. Projection on the inner liner on the die side for the sealing face (conical/flat) of at least 10 mm.
7. Heating elements in the centre of the container mantle minimum distance of 80 mm.
8. Power connector for heating system on stem side (KCPC).
9. Container is as large as possible $d > 2$; container starts with inner liner $> 50 \text{ mm}$ wall thickness.
10. Air cooling on the intermediate liner due to product and customer requirements or to reduce temper effects and plastic deformation on the container.

Typical wear on containers on heavy metal extrusion and possible solutions



- **Thermal shock cracks in inner liner bores:** Reduction of cracks by using SA718 inner liners.
- **Deformation of conical sealing face:** Check cleaning intervals in press operations; Use of SA718 inner liners.
- **Abrasion of inner liner bore during the extrusion process:** Use of SA718 inner liners with > 300 MPa higher strength compared to a standard HWF inner liner.

Comparison of lifetime for HWF- and SA718- inner liners during extrusion



HWF (1000 – 1150 MPa) after 30,000 Cu billets, coarse network of cracks with eruptions




SA718 (1250 – 1400 MPa) after 150,000 Cu billets, fine network of cracks

Temper effect and its plastic deformation across the container length



Changeover of containers to air cooling; use of high temperature strength materials and HTR intermediate liners in combination with SA718 inner liners

Temper effect and its plastic deformation across the container length as a diagram

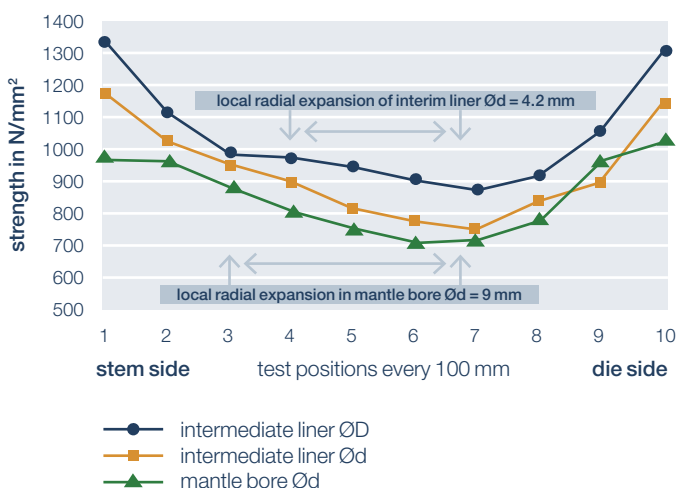

Production processes

Melting

Forging

Heat treatment

Mechanical processing

Vacuum hardening

Surface treatment

Products

Hot-work steels

Cold-work steels

Drop-forging steels

Plastic mould steels

Special materials

Industries

Pressure die casting

Extrusion

Drop forging

Pipe technology

Plastics technology

Hot-press hardening

Special applications



Kind & Co., Edelstahlwerk, GmbH & Co. KG

Bielsteiner Str. 124-130 · D-51674 Wiehl

Fon. +49 (0) 22 62 / 84-0 · Fax +49 (0) 22 62 / 84-175

info@kind-co.de · www.kind-co.de